

The following sample(s) was/ were submitted and identified on behalf of the client as:

Sample Name : Artificial hedge

SGS Ref. No. : TJHG1501000228SD

Product or Lot No. : G0602A001

Date of Receipt : Jan 26, 2015

Testing Start Date : Jan 26, 2015

Testing End Date : Feb 03, 2015

Test result(s) : For further details, please refer to the following page(s)

Signed for SGS-CSTC Standards Technical Services(Tianjin) Co., Ltd

Linda Yuan

Authorized signatory



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.



### Summary of Results:


No.	Test Item	Test Method	Result	Conclusion
1	Light Ageing Test-UV Exposure	ASTM G154-12a Cycle1	See result	1

Note: Pass : Meet the requirements;

Fail: Does not meet the requirements;

/: Not Apply to the judgment.

### Original Sample Photo:

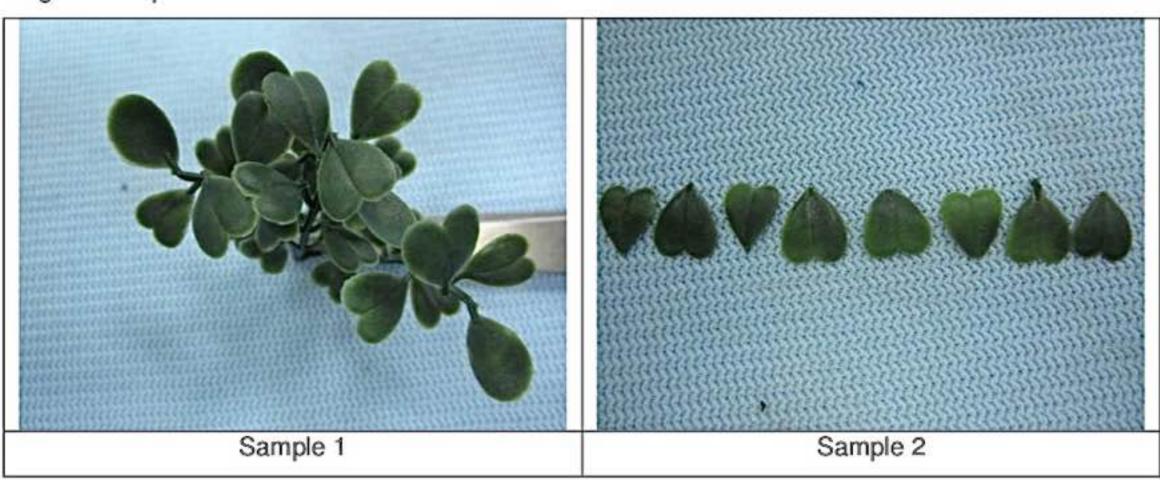



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <a href="http://www.sgs.com/en/Terms-and-Conditions.aspx">http://www.sgs.com/en/Terms-and-Conditions.aspx</a> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <a href="http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx">http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx</a>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

retained for 30 days only .

Attention: To check the authenticity of testing finspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com



Test Item: Light Ageing Test-UV Exposure

Sample Description: See photo

Test Method: ASTM G154-12a Cycle1 & ISO 105-A02:1993/Cor.2:2005

Test Condition:

Exposure cycle:

ASTM G154-12a cycle 1

Lamp type: UVA-340

8h UV at (60±3)°C BPT, 0.89W/(m2•nm)@340nm

4h condensation at (50±3)°C BPT

Exposure duration: 60h

#### Test Result:

Sample	Appearance	Grey scale
1	No visual change	Rating 4-5
2	No visual change	Rating 4-5

#### Note:

- According to ISO 105-A02:1993/Cor.2:2005, the grey scale was determined under the D65 standard light, with scale 5 as the best and scale 1 as the worst.
- The results were carried out within 1 hour after above specified durations for the intermediate inspection as well as at the end of the exposure.
- 3. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.




This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN\_Doccheck@sgs.com

www.sgsgroup.com.cn



#### Test Photo:

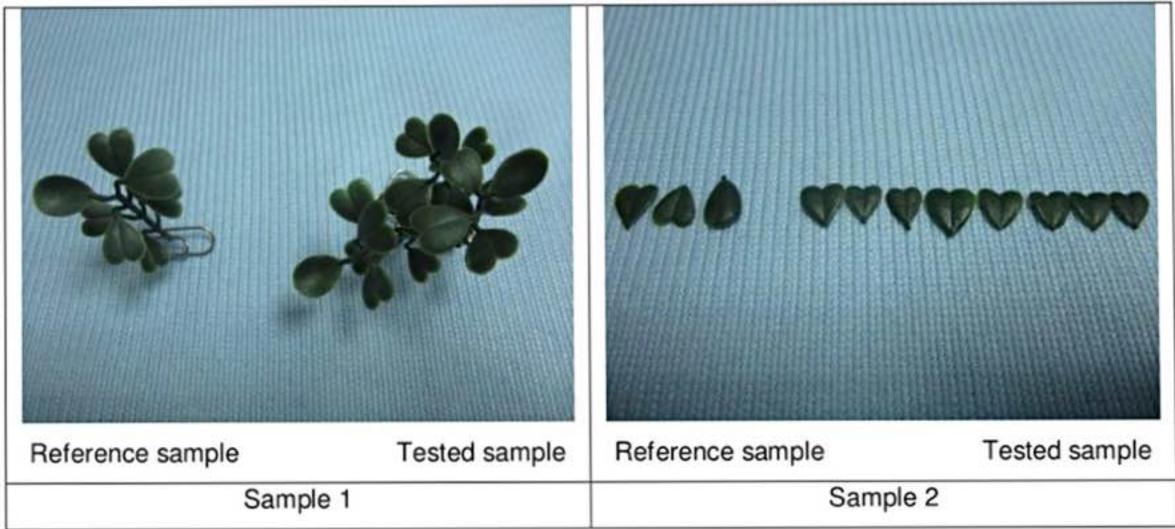

\*\*\*\*\*\*\* End of report\*\*\*\*\*\*\*



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this documnt is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) \$307 1443, or email: CN\_Doccheck⊗sgs.com

No. 555, Central Avenue, TAEA, China. 300345 中国·天津·空港经济区中心大道555号 邮编: 300345 t (86-22) 59803788 t (86-22) 59803788 f (86-22) 59803777 f (86-22) 59803777 www.sgsgreup.com.cn e sgs.china@sgs.com